

Comment on “Superconducting anisotropy and evidence for intrinsic pinning in single crystalline MgB₂”

M. Angst,^{1,*} R. Puzniak,² A. Wisniewski,² J. Roos,³ H. Keller,³ and J. Karpinski¹

¹*Solid State Physics Laboratory ETH, 8093 Zürich, Switzerland*

²*Institute of Physics, Polish Academy of Sciences, Al. Lotnikow 32/46, 02-668 Warsaw, Poland*

³*Physik-Institut, Universität Zürich, 8057 Zürich, Switzerland*

(Dated: February 6, 2008)

In a recent paper [Phys. Rev. B **66**, 012501 (2002)], torque data measured on a MgB₂ single crystal in fields from 10 to 60 kOe at 10 K were presented. The authors obtained the anisotropy γ by fitting a theoretical expression to the data and concluded that the anisotropy is field independent $\gamma \approx 4.3$. They also reported the observation of “intrinsic pinning”, which they take as experimental evidence for the occurrence of superconductivity in the boron layers. In this comment, we discuss the range of validity of the theoretical expression used by the authors and show that the conclusion of a field independent anisotropy does not hold. Furthermore, we present torque data measured on two crystals of MgB₂, establishing the extrinsic nature of the peak in the irreversible torque observed in some crystals.

PACS numbers: 74.25.Ha, 74.60.-w

In a recent report,¹ Takahashi *et al.* presented torque measurements performed on a single crystal of MgB₂. The authors concluded that the anisotropy $\gamma \approx 4.3$ is field independent at 10 K, in contrast to an earlier finding² of a pronounced field dependence of γ at higher temperatures. The main purpose of this comment is to show that the conclusion in Ref. 1 of a field independent γ at 10 K does not hold, since the expression used in the analysis is not applicable to all of the data.

In Ref. 1, the experimental data for angular torque dependences in different fields were described by a formula developed by Kogan,³ which in CGS units has the following form:

$$\tau = -\frac{\Phi_0 H V}{64\pi^2 \lambda_{ab}^2} \left(1 - \frac{1}{\gamma^2}\right) \frac{\sin 2\theta}{\epsilon(\theta)} \ln \left(\frac{\eta H_{c2}^{\parallel c}}{\epsilon(\theta) H} \right), \quad (1)$$

where $\epsilon(\theta) = (\cos^2 \theta + \sin^2 \theta / \gamma^2)^{1/2}$, θ is the angle between the applied magnetic field and the c -axis of the crystal, $\gamma = (m_c^* / m_{ab}^*)^{1/2}$ is the effective mass anisotropy, $H_{c2}^{\parallel c}$ is the upper critical field parallel to the c -axis, λ_{ab} is the in-plane penetration depth, V is the volume of the crystal, Φ_0 is the flux quantum, and η is a constant of the order of unity depending on the vortex lattice structure. Equation (1) for the angular dependence of the reversible torque was derived on the basis of the anisotropic London model, valid in the limits of fields $H_{c1} \ll H \ll H_{c2}$, the latter condition is important to exclude vortex core overlap.

In the analysis, Takahashi *et al.* did not fit to the experimental data all of the parameters of Eq. (1), but assumed the value of $\eta H_{c2}^{\parallel c}$ to be fixed and equal to 60 kOe, because earlier measurements on a MgB₂ crystal from the same source indicated an upper critical field parallel to the c -axis located in this region at low temperatures.⁴ It should be mentioned, however, that these H_{c2} values were determined from resistivity measurements. Later bulk

measurements on single crystals^{2,5,6,7,8} found a lower $H_{c2}^{\parallel c}$ value in the region of 30 – 35 kOe, in contrast to the resistivity results, which are affected by surface effects.^{5,7} Furthermore, the data presented by Xu *et al.* indicate an anisotropy of the upper critical fields of 2.6, a much lower value than the estimation of Takahashi *et al.*. A possible reason of the large discrepancy is an overestimation of $H_{c2}^{\parallel c}$ by Xu *et al.* due to alignment problems. Since different assumptions on the value of the parameter $\eta H_{c2}^{\parallel c}$ yield different anisotropies γ from a fit of Eq. (1), it would be interesting to see what values of γ would result with different assumptions of $\eta H_{c2}^{\parallel c}$.

Problematic, especially if $H_{c2}^{\parallel c}$ is smaller than 60 kOe, is the application of Eq. (1) for data measured in fields up to 60 kOe, particularly since data measured in the whole angular region from 0 to 180 deg are used in the fits. Even if $H_{c2}^{\parallel c}$ is indeed about 60 kOe, the condition $H \ll H_{c2}$ for the validity of the London model, and thus of Eq. (1) is not fulfilled for all data analyzed. It should be visible in the data if $H > H_{c2}^{\parallel c}$, since in this case the superconducting torque is zero for angles for which $H > H_{c2}(\theta)$, as can be seen, for example, in Fig. 1 of Ref. 2. In the data presented in Ref. 1, the relatively low signal-to-noise ratio makes a corresponding direct unambiguous conclusion about the location of $H_{c2}^{\parallel c}$ difficult. Nevertheless, in our opinion Fig. 2 of Ref. 1 indicates that both the data measured in 60 and in 50 kOe are above H_{c2} for field directions close to the c -axis. This may or may not be the case for the data measured in 40 kOe as well. We therefore think that Eq. (1) is not applicable for the analysis of the data presented in Fig. 2 of Ref. 1. Even the data obtained in $H = 30$ kOe (Fig. 1 of Ref. 1) may not be sufficiently below $H_{c2}^{\parallel c}$ to yield a proper γ value from a fit of Eq. (1) as there can still be a certain degree of core overlap.

The data measured in 10 kOe indicate a lower

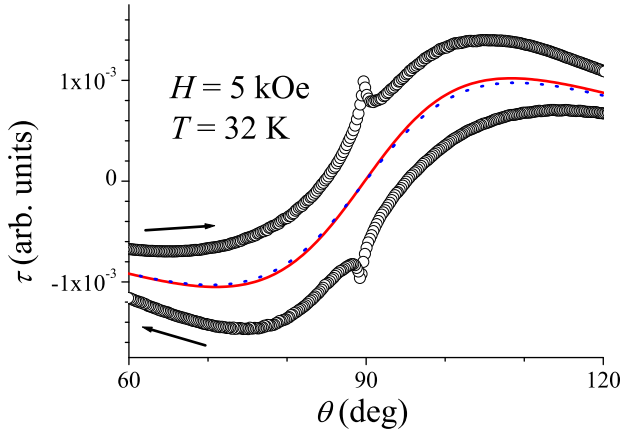


FIG. 1: Torque τ of a MgB_2 single crystal⁹ vs angle θ at 32 K in 5 kOe. Shown are the measured data ($\circ$), a fit of Eq. (1) to $(\tau_{\text{inc}} + \tau_{\text{dec}})/2$, in the range of angles as shown (full line), and a fit of Eq. (1) to the shaken torque (broken line).

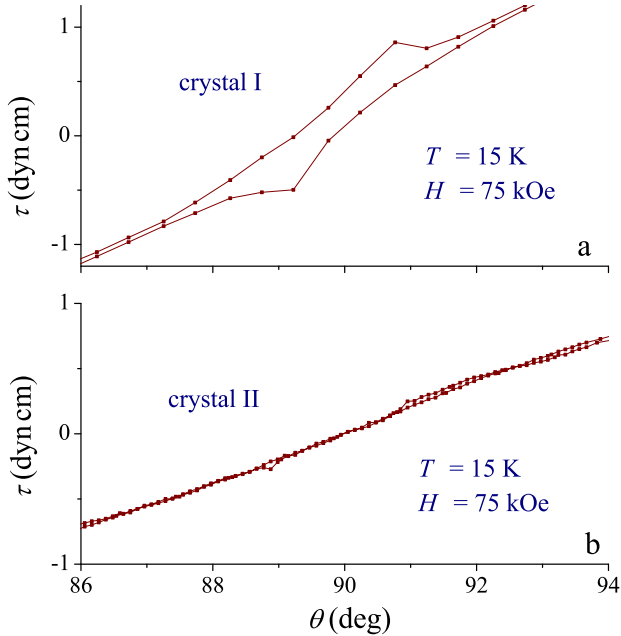


FIG. 2: Torque τ vs angle θ near $H\parallel ab$ for two different MgB_2 crystals, one showing a peak in the irreversible torque near $H\parallel ab$ (a), the other one not showing such a peak (b).

anisotropy. As Takahashi *et al.* correctly note, simple arithmetic averaging of the torque measured for clockwise (τ_{inc}) and counterclockwise (τ_{dec}) change of the field direction not necessarily yields the correct equilibrium reversible torque when there is substantial irreversibility. However, in a torque study on $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, Willemin *et al.*¹⁰ observed that γ extracted from the correct reversible torque, obtained with “shaking” the vortices by a small perpendicular ac field,¹¹ had a lower value than γ extracted from $(\tau_{\text{inc}} + \tau_{\text{dec}})/2$. Thus, substantial irreversibility leads to an overestimation of the anisotropy

γ . There is no hard proof that it has to be like this always. To check the situation in MgB_2 , we performed a similar experiment. Figure 1 shows $\tau(\theta)$ data measured on a MgB_2 single crystal⁹ in 5 kOe at 32 K and the corresponding fit of Eq. (1) to $(\tau_{\text{inc}} + \tau_{\text{dec}})/2$. The reversible torque data obtained by “shaking” can be seen in Fig. 5 of Ref. 2.¹² In this case of data obtained with a “shaking” experiment, an anisotropy of $\gamma \simeq 3.2$ was fitted, together with $\eta H_{c2}^{\parallel c}/H \simeq 1.75$. When the “unshaken” data of Fig. 1 are fitted, while keeping $\eta H_{c2}^{\parallel c}/H \simeq 1.75$, $\gamma \simeq 3.4$ is obtained, i.e., a higher value. If $\eta H_{c2}^{\parallel c}/H$ is instead fitted as well, even a higher anisotropy, $\gamma \simeq 3.6$ is obtained. If the whole angular range from 0 to 180 deg is fitted, the fitted γ is also 3.6, but to compare with the shaken data it is better to use the same range of angles. Either way, the values of γ obtained from non-shaken data are higher and it seems therefore reasonable to conclude that the value $\gamma(10 \text{ kOe}) \simeq 2.84$ obtained in Ref. 1 represents an upper limit of the real anisotropy.

If the description of the experimental data from 30 to 60 kOe by Eq. (1) is unreliable, the analysis of the data is thus limited to 10 kOe with the value of γ given in Ref. 1 representing an upper limit, and to 20 kOe. In this case, we can conclude that the data presented in Ref. 1 indicate a field dependent effective anisotropy parameter γ , in accordance with the conclusions of Ref. 2.

Takahashi *et al.* observed a peak in the irreversible torque at 10 K in 10 kOe for field directions close to the ab -plane. They interpret the existence of such a peak as evidence of intrinsic pinning (lock-in effect) and thus as experimental evidence that superconductivity occurs in the boron layers, in analogy to the layered cuprate HTSC. The existence of a similar peak was observed on another single crystal of MgB_2 (see Fig. 5 of Ref. 2) and also attributed to the lock-in effect, although no further conclusions were drawn. However, from subsequent studies of different single crystals of MgB_2 , we found that such a peak is present in some MgB_2 crystals, but not in all: Figure 2 presents $\tau(\theta)$ near $H\parallel ab$ for two different crystals, one showing a large lock-in effect, and the other one practically none. On the base of this observation, we conclude that the presence of the peak is not an intrinsic property of MgB_2 . This is in accordance with the estimation that the ratio of the coherence length perpendicular to the layers ξ_c over the layer separation d (estimated by the c -axis of the unit cell) is larger than 1. A ratio $\xi_c/d > 1$ implies that MgB_2 is within the anisotropic 3D limit, and therefore a lock-in effect and intrinsic pinning should not be observed. The peak for $H\parallel ab$ observed in some MgB_2 crystals may be caused, for example, by a small amount of stacking faults.¹³ This problem will be discussed in more detail in one of our next papers. As a non-intrinsic feature, the observed peak for $H\parallel ab$ can not prove the occurrence of superconductivity in the boron layers.

-
- * Email: angst@phys.ethz.ch
- ¹ K. Takahashi, T. Atsumi, N. Yamamoto, M. Xu, H. Kitazawa, and T. Ishida, Phys. Rev. B **66**, 012501 (2002).
 - ² M. Angst, R. Puzniak, A. Wisniewski, J. Jun, S. M. Kazakov, J. Karpinski, J. Roos, and H. Keller, Phys. Rev. Lett. **88**, 167004 (2002).
 - ³ V. G. Kogan, Phys. Rev. B **38**, 7049 (1988).
 - ⁴ M. Xu, H. Kitazawa, Y. Takano, J. Ye, K. Nishida, H. Abe, A. Matsushita, N. Tsujii, and G. Kido, Appl. Phys. Lett. **79**, 2779 (2001).
 - ⁵ A. Sologubenko, J. Jun, S. Kazakov, J. Karpinski, and H. Ott, Phys. Rev. B **65**, 180505(R) (2002).
 - ⁶ M. Zehetmayer, M. Eisterer, H. W. Weber, J. Jun, S. M. Kazakov, J. Karpinski, and A. Wisniewski, cond-mat/0204199.
 - ⁷ U. Welp, G. Karapetrov, W. K. Kwok, G. W. Crabtree, C. Marcenat, L. Paulius, T. Klein, J. Marcus, K. H. P. Kim, C. U. Jung, *et al.*, cond-mat/0203337.
 - ⁸ L. Lyard, P. Samuely, P. Szabo, C. Marcenat, T. Klein, K. H. P. Kim, C. U. Jung, H.-S. Lee, B. Kang, S. Choi, *et al.*, cond-mat/0206231.
 - ⁹ Sample A of Ref. 2.
 - ¹⁰ M. Willemin, C. Rossel, J. Hofer, H. Keller, A. Erb, and E. Walker, Phys. Rev. B **58**, R5940 (1998).
 - ¹¹ To speed up their relaxation into equilibrium. See Ref. 10 for details.
 - ¹² Note that the angle values in the insets of Fig. 5 correspond to the angle between H and the ab -plane.
 - ¹³ Y. Zhu, L. Wu, V. Volkov, Q. Li, G. Gu, A. R. Moodenbaugh, M. Malac, M. Suenaga, and J. Tranquada, Physica C **356**, 239 (2001).